Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

AWTA PRODUCT TESTING

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400

#### **TEST REPORT**

| Client : | Orafol Australia | Test Number | : | 21-002731  |
|----------|------------------|-------------|---|------------|
|          | 8 Blanck Street  | Issue Date  | : | 11/06/2021 |
|          | Ormeau QLD 4208  | Print Date  | : | 11/06/2021 |
|          |                  |             |   |            |

| Sample Description | Clients Ref : "Orajet 3164"<br>Flexible self-adhesive film |  |
|--------------------|--|--|
|                    | Colour : White<br>End Use : Wall Covering                  |  |
|                    | Nominal Composition :PVCNominal Thickness :100 micron      |  |

| AS/NZS 3837-1998 | Method of |
|------------------|-----------|
|                  | Consumpt  |

Date Tested Face Tested

of Test for Heat and Smoke Release Rates for Materials and Products using an Oxygen otion Calorimeter 11-06-2021 FACE Specimen Maan ~

|                                  | 1    | 2    | 3    | iviean                 |
|----------------------------------|------|------|------|------------------------|
| Average Heat Release Rate        | 21.8 | 23.1 | 22.8 | 22.6 kW/m <sup>2</sup> |
| Average Specific extinction area | 46.5 | 43.3 | 57.8 | 49.2 m²/kg             |

(according to Specification C1.10 of the Building Code of Australia)

Horizontal Test orientation :

|                                  | Specimen |       |       |       |       |
|----------------------------------|----------|-------|-------|-------|-------|
|                                  | 1        | 2     | 3     | Mean  |       |
| Irradiance                       | 50       | 50    | 50    | 50    | kW/m² |
| Exhaust flow rate                | 0.024    | 0.024 | 0.024 | 0.024 | m³/s  |
| Time to sustained flaming        | 33       | 25    | 30    | 29    | sec   |
| Test duration                    | 230      | 220   | 219   | 223   | sec   |
| Peak heat release after ignition | 76.9     | 77.1  | 79.9  | 78.0  | kW/m² |
| Average heat at 60 s             | 41.7     | 45.6  | 43.4  | 43.6  | kW/m² |
| Average heat at 180 s            | 22.8     | 24.2  | 23.4  | 23.5  | kW/m² |
| Average heat at 300 s            | n/a      | n/a   | n/a   | n/a   | kW/m² |

152764

52011

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved C



the Managing Director of AWTA Ltd.

Accredited for compliance with ISO/IEC 17025 - Testing

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approv

Page 1 of 8

AFL A. JACKSON B.Sc.(Hons)

Chris Campbell APPROVED SIGNATORY

Lby

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

AWTA Product Testing

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400

# **TEST REPORT**

| Client :                                | Orafol Australia<br>8 Blanck Street<br>Ormeau QLD 4208 |      |      |      | Number :<br>Date :<br>Date : | 21-002731<br>11/06/2021<br>11/06/2021 |
|---|--|------|------|------|------------------------------|---------------------------------------|
| Total heat rele                         | eased  | 4.3  | 4.6  | 4.3  | 4.4                          | MJ/m <sup>2</sup>                     |
| Average effective heat of combustion    |  | 4.1  | 4.1  | 4.2  | 4.1                          | MJ/kg                                 |
| Initial thickness                       |  | 11   | 11   | 11   | 11.0                         | mm                                    |
| Initial mass                            |  | 60.2 | 60.4 | 59.6 | 60.1                         | g                                     |
| Mass remaining                          |  | 51.8 | 51.7 | 51.2 | 51.6                         | g                                     |
| Mass percentage pyrolysed               |  | 14.0 | 14.4 | 14.1 | 14.2                         | %                                     |
| Mass loss                               |  | 1.0  | 1.1  | 1.0  | 1.1                          | kg/m²                                 |
| Average rate of mass loss               |  | 5.3  | 5.5  | 5.5  | 5.5                          | g/m².s                                |
| Additional Ob                           | servations   | NONE |      |      |                              |                                       |
| Difficulties Encountered during Testing |  | NONE |      |      |                              |                                       |

Tests were conducted with a wire grid placed over the sample during testing. This was done to contain intumescing sample within the sample holder.

These test results relate only to the behaviour of the product under the conditions of the test, they are not intended to be the sole criterion for assessment of performance under real fire conditions.

The results of these fire tests may be used to directly assess fire hazard, but it should be recognised that a single test method will not provide a full assessment of the fire hazard under all fire conditions.

Each specimen was self adhered to 10mm thick plasterboard prior to testing

152764

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved

#### 52011



Accredited for compliance with ISO/IEC 17025 - Testing

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

Chris Campbel



Page 2 of 8



C

Chris Campbel APPROVED SIGNATORY

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051


Phone (03) 9371 2400

### **TEST REPORT**

| Client : | Orafol Australia |  |
|----------|------------------|--|
|          | 8 Blanck Street  |  |
|          | Ormeau QLD 4208  |  |

21-002731 Test Number : Issue Date 11/06/2021 : 11/06/2021 **Print Date** :

Specimen : 1

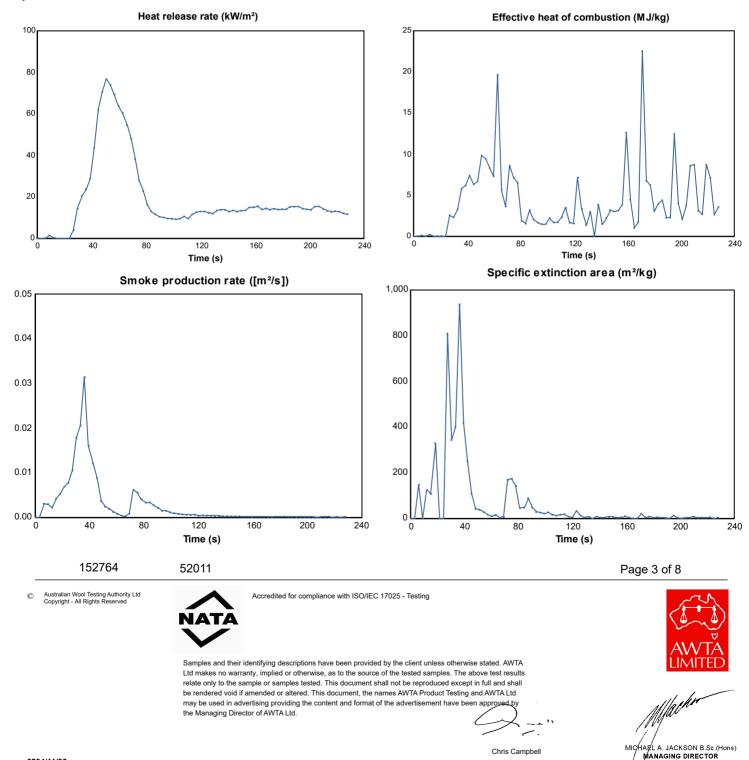

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031


P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400

# **TEST REPORT**

Orafol Australia Client : 8 Blanck Street Ormeau QLD 4208

21-002731 Test Number : Issue Date 11/06/2021 : 11/06/2021 **Print Date** :

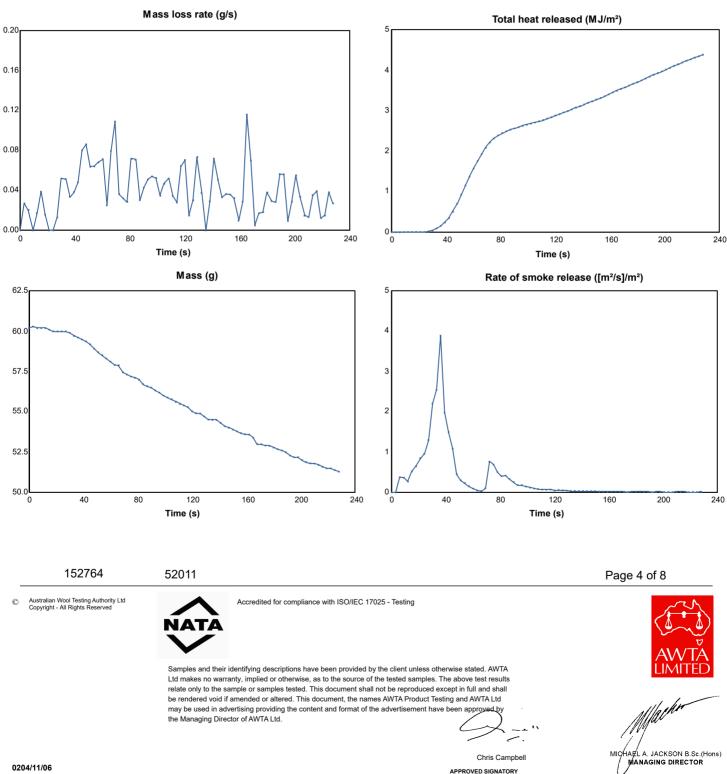

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400

### **TEST REPORT**

| Test Number | : | 2 |
|-------------|---|---|
| Issue Date  | : | 1 |
| Print Date  | : | 1 |

21-002731 11/06/2021 11/06/2021


2 Specimen :

Client :

Orafol Australia

8 Blanck Street

Ormeau QLD 4208

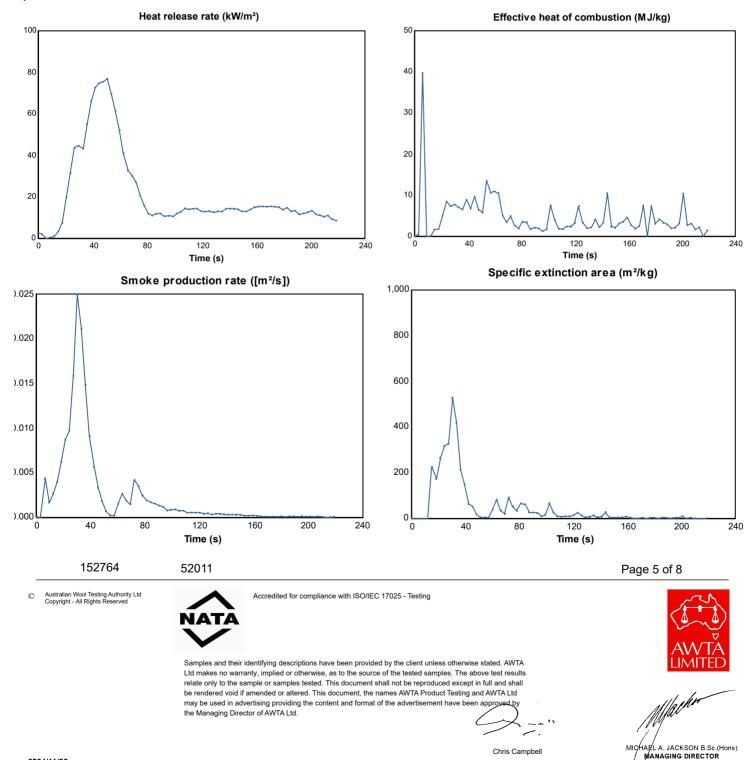

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051


Phone (03) 9371 2400

# **TEST REPORT**

Client : Orafol Australia 8 Blanck Street Ormeau QLD 4208 
 Test Number
 :
 21-002731

 Issue Date
 :
 11/06/2021

 Print Date
 :
 11/06/2021

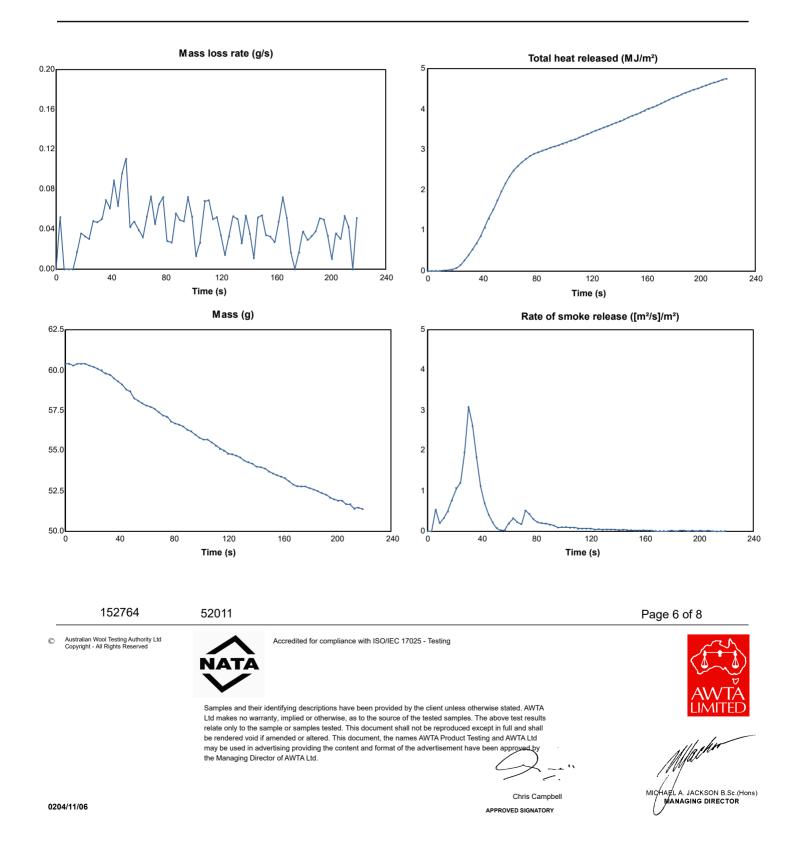

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400


### **TEST REPORT**

| Orafol Australia |  |  |
|------------------|--|--|
| 8 Blanck Street  |  |  |
| Ormeau QLD 4208  |  |  |

| Test Number | : | 21-002731  |
|-------------|---|------------|
| Issue Date  | : | 11/06/2021 |
| Print Date  | : | 11/06/2021 |

3 Specimen :

Client :

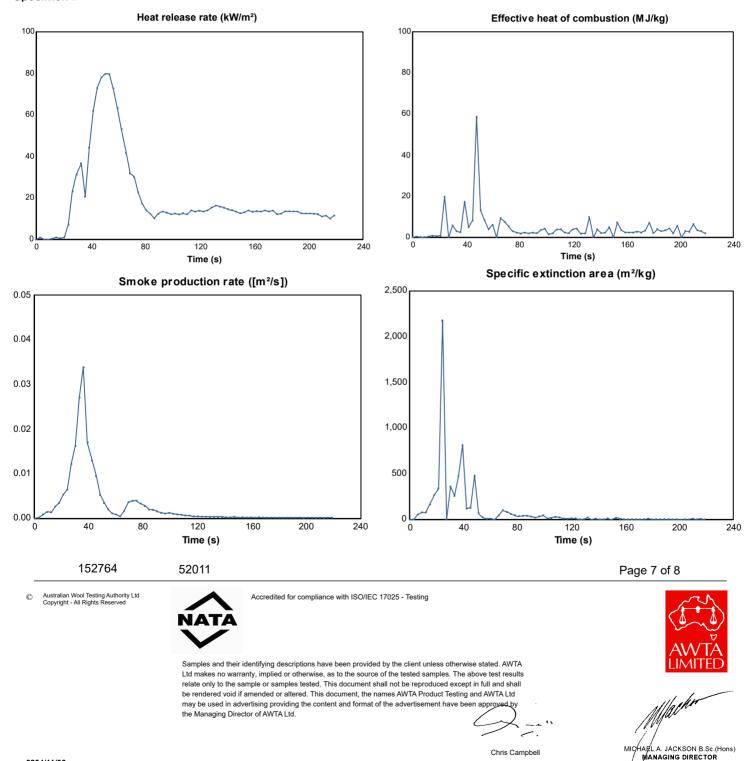

Chris Campbel APPROVED SIGNATORY

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing

A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031

P.O Box 240, North Melbourne, Victoria 3051

Phone (03) 9371 2400

# **TEST REPORT**

Orafol Australia Client : 8 Blanck Street Ormeau QLD 4208

21-002731 Test Number : Issue Date 11/06/2021 : 11/06/2021 **Print Date** :

